

Phase-transitions in isotropic extreme type-II superconductors

S-K. Chin, A. K. Nguyen and A. Sudbø

Department of Physics, Norwegian University of Science and Technology, Trondheim, 7034 Norway.
(February 1, 2008)

Using large scale Monte Carlo simulations on a uniformly frustrated 3DXY model, we report a *first order* vortex lattice melting transition in clean, *isotropic* extreme type-II ($\kappa \rightarrow \infty$) superconductors. This work clarifies an important issue: the unpinned vortex liquid is always *incoherent* with no phase coherence in any directions for all anisotropies. Previous claims of a disentangled vortex liquid for isotropic superconductors based on simulations, are due to finite size effects. We explicitly show that the effective vortex-line tension vanishes precisely at the superconducting phase transition in zero magnetic field. This loss of line tension is accompanied by an abrupt change in the connectivity of the vortex tangle across the superconductor. We also obtain results indicating that the connectivity of the vortex tangle changes in a similar way even in finite magnetic field, and suggest that this could also be associated with a genuine phase-transition.

I. INTRODUCTION

Since the discovery of copper oxide based high temperature superconductors (HTSC)¹, which are of the extreme type-II variety, there has been great interest in their phenomenological phase diagrams. Abrikosov's mean-field description², which is valid for conventional low temperature superconductors, is expected to be modified by the strong thermal fluctuations in HTSC. Extensive research in both theory, numerical simulations, and experiments over the years have resulted in a general consensus on some of the fundamental issues. The current understanding of HTSC in a uniform magnetic field \mathbf{B} is as follows. In the absence of any pinning disorder, the low temperature Abrikosov vortex lattice phase melts into a vortex liquid via a first order transition at the temperature T_m . The Abrikosov vortex lattice phase is characterized by a transverse triangular crystalline order and a finite longitudinal phase coherence.

However, recently there has been some debate about the nature of the vortex liquid which the Abrikosov vortex lattice melts into as temperature increases. Numerous simulations using the 3DXY model³⁻⁶, London⁷ and Lowest Landau Level approximations⁸ have indicated that the vortex liquid is *incoherent*, i.e. the phase coherence or superfluid density in any direction, is zero. The crystalline order and phase coherence are destroyed simultaneously at the melting transition. This scenario has been supported by experiments on high quality YBCO crystals⁹. Other simulations using the 3DXY model¹⁰⁻¹² have suggested that the longitudinal phase coherence persists above the melting transition and only vanishes at a higher "entanglement" temperature T_E . In this scenario, the vortex liquid at $T_m < T < T_E$ would be disentangled with relatively straight vortex lines. For $T > T_E$, it was claimed that larger thermal fluctuations causes the vortex lines to be entangled with a concomitant loss of global phase coherence¹⁰⁻¹².

Previously, a vortex liquid with nonzero longitudinal

phase-coherence, or superfluid density, was found in simulations on an isotropic system^{10,12}. More recently¹², it has been proposed that for large B , T_m and T_E merge into a single transition whereas for small \mathbf{B} they are well separated. The authors found that for an isotropic system, the crossover between the two regimes is at a filling fraction $1/18 < f < 1/6$, where the precise definition of $f \propto B$ will be given shortly. However, these simulations were performed on rather small systems. In the present work, we have performed similar simulations on a much larger system, and found an exclusively incoherent vortex liquid down to $f = 1/60$. This implies that the only thermodynamically stable vortex liquid phase, is one which has zero longitudinal superfluid density, with full translational and rotational symmetries and zero phase coherence in all directions. We are therefore led to the conclusion that the recently discussed¹² crossover between the phase-coherent vortex liquid and the phase-incoherent vortex liquid is a numerical artifact.

The organization of this paper is as follows. In Section II we first briefly review the model used in the simulations, and the quantities we calculate. In Section III we discuss our results and their implications. In Section IV we provide a summary and conclusion.

II. MODEL

We use a uniformly frustrated 3DXY model on a cubic lattice to describe an isotropic, extreme type-II superconductors in a magnetic field. The London model for superconductors can be readily derived from the phenomenological Ginzburg-Landau (GL) model with the approximation that the amplitude of the local complex order parameter $\psi = |\psi| \exp[i\theta]$, is fixed. The Hamiltonian H of the London model consists of degrees of freedom in the phase $\theta(\mathbf{r})$ and the gauge vector potential $\mathbf{A}_{vp}(\mathbf{r})$ associated with the magnetic induction \mathbf{B} inside the system, i.e. $H = H[\{\theta(\mathbf{r}), \mathbf{A}_{vp}(\mathbf{r})\}]$.

For an isotropic extreme type-II superconductor, the penetration depth λ is much larger than the coherence length ξ such that the GL parameter $\kappa = \lambda/\xi \rightarrow \infty$. This means that the magnetic fields surrounding the vortex lines strongly overlap with one another giving a spatially smooth \mathbf{B} . This condition is ensured in the regime where $\mathbf{B} > \mathbf{B}_{c1}$. In other words, the fluctuations of $\mathbf{A}_{vp}(\mathbf{r})$ on the length scale of ξ are negligible compared to the fluctuations of $\theta(\mathbf{r})$. Therefore, we can further simplify the problem by dropping the degrees of freedom of $\mathbf{A}_{vp}(\mathbf{r})$ from the Hamiltonian H , and fix B equal to the external applied magnetic field. The resulting Hamiltonian $H = H[\{\theta(\mathbf{r})\}]$ is the 3DXY model. This $\kappa \rightarrow \infty$ (or frozen gauge) approximation has been widely used as a phenomenological model for superconductors. Note that, within this model, the system has no *magnetic flux lines*, since there can be no tubes of confined magnetic flux when $\lambda \rightarrow \infty$. The system only exhibits *vortex lines*.

In order to perform numerical simulations on the resulting model, we discretize the model on a 3D cubic lattice with grid spacing ξ . The dimensionless Hamiltonian of this lattice model is given by^{13,11,4}

$$H[\{\theta(\mathbf{r})\}] = -J_0 \sum_{\mathbf{r}, \alpha=x,y,z} \cos \left(j_\alpha[\theta(\mathbf{r})] \right) \quad (1)$$

where $J_0 = \Phi_0^2 \xi / 4\pi^2 \mu_0 \lambda^2$ is the isotropic coupling energy, $\Phi_0 = \hbar\pi/e$ is the flux quanta and μ_0 is the permeability of a vacuum in SI units. The dimensionless vector \mathbf{r} labels the position of an arbitrary grid point. We define the gauge-invariant phase difference $j_\alpha(\mathbf{r})$ as

$$j_\alpha(\mathbf{r}) \equiv \theta(\mathbf{r} + \mathbf{e}_\alpha) - \theta(\mathbf{r}) - \frac{2\pi\xi}{\Phi_0} \int_{\mathbf{r}}^{\mathbf{r}+\mathbf{e}_\alpha} d\mathbf{r}' \cdot \mathbf{A}_{vp}(\mathbf{r}') \quad (2)$$

where \mathbf{e}_α is the unit vector along the α -axis. The convention is that $j_\alpha(\mathbf{r})$ “flows” from the grid at \mathbf{r} to $\mathbf{r} + \mathbf{e}_\alpha$. In this model, it is natural to define a dimensionless temperature $\tilde{T} = k_B T / J_0$. The magnetic induction \mathbf{B} is conveniently represented by the filling fraction

$$f = \frac{B\xi^2}{\Phi_0}. \quad (3)$$

In this paper, we perform a Monte Carlo simulation on an isotropic system with $V = N_x \times N_y \times N_z$ number of grid points. The aim of our numerical simulations is to identify possible thermodynamic phases (i.e. vortex lattice or liquid, etc.) and phase transitions (first order or continuous) or crossovers associated with them. Specifically, we are interested in calculating the internal energy, specific heat, structure factor, and helicity moduli. These thermodynamic quantities and their physical significance will be discussed next. In addition, we introduce and define a quantity O_L which we denote the vortex-path probability, and discuss some of its physical implications.

A first order transition is indicated by a δ -function anomaly in the specific heat, equivalently a discontinuous jump in the internal energy. On the other hand, the

hallmark of a continuous transition is a jump in the specific heat, modified by fluctuation contributions to the anomaly, and a continuous internal energy. The internal energy per site is obtained by averaging H in Eq. (1) over the thermal equilibrium states, normalized by the total number of grids, i.e. $E = \langle H \rangle / V$. We define a dimensionless specific heat per site C using the standard fluctuation theorem of a classical system with Gibbs distribution¹⁴:

$$C = \frac{\langle H^2 \rangle - \langle H \rangle^2}{V(k_B T)^2} \quad (4)$$

A convenient and widely used quantity to probe the *global* phase coherence of the system is the helicity modulus, which is proportional to the second derivative of the free energy associated with Eq. (1) with respect to an infinitesimal phase twist^{10,3}. On a square lattice, the dimensionless helicity modulus Υ_α can be written as

$$\Upsilon_\alpha = \frac{1}{V} \left\langle \sum_{\mathbf{r}} \cos j_\alpha - \frac{1}{T} \left| \sum_{\mathbf{r}} \sin j_\alpha \right|^2 \right\rangle. \quad (5)$$

Υ_α measures the “stiffness” of θ with respect to twisting along the α -direction. If $\Upsilon_\alpha > 0$ then θ is stiff in the α -direction, or more precisely, there is *global* phase coherence or superconducting response in that direction. By tracking the temperature at which Υ goes to zero, one can determine the superconducting-normal metal transition temperature of the system. In the mixed phase $\Upsilon_\parallel > 0$ and $\Upsilon_\perp = 0$, where the subscripts \parallel and \perp denote the directions longitudinal and transverse to \mathbf{B} , respectively.

The structure factor probes the transverse crystalline order of the vortex system. We adopt a conventional definition⁴:

$$S(\mathbf{k}_\perp) = \frac{1}{(fV)^2} \left\langle \left| \sum_{\mathbf{r}} v_\perp(\mathbf{r}) \exp(i\mathbf{k}_\perp \cdot \mathbf{r}) \right|^2 \right\rangle \quad (6)$$

where \mathbf{k}_\perp is a two-dimensional reciprocal vector and $v_\alpha(\mathbf{r})$ is the local vorticity measured on the dual square lattice grid^{3,4}, composed of the centers of every direct unit cell. A crystalline ordered phase is characterized by $S(\mathbf{k}_0) > 0$ (or Bragg peaks) where \mathbf{k}_0 are the *discrete* set of reciprocal lattice vectors associated with the crystal structure. On the other hand, $S(\mathbf{k})$ for a phase with full rotational invariance exhibits ring patterns.

At a fixed temperature, the equilibrium configurations are generated by making random changes to $\theta(\mathbf{r})$ at each grid-point via the the Metropolis algorithm. This is equivalent to randomly changing all the six j_α attached to each grid-point. To ensure conservation of vorticity in each unit cell, j_α has to be in the range $[-\pi, \pi)$. Addition of $\pm 2\pi$ shall be administrated to bring j_α back into range at every Monte Carlo step. *This procedure introduces vortex-loops into the system. Such loops are*

the elementary topological excitation of the model. Periodic boundary conditions (PBC) are imposed on j_α such that $j_\alpha(\mathbf{r} + N_\mu \mathbf{e}_\mu) = j_\alpha(\mathbf{r})$ for $\mu = (x, y, z)$. More details about the Monte Carlo procedure may be found in Refs. 3,4.

We define O_L as the probability of finding a directed vortex path threading the entire system transverse to the induction B , *without using the PBC along the field direction*¹⁵. It is obtained by computing the number N_V of times we find *at least one* such path threading the system in any direction $\perp B$ in N_P different phase-configurations, normalized by N_P , i.e. $O_L = N_V/N_P$. The fact that $O_L = 0$ implies that there is no connected path of vortex segments that threads the entire system in the transverse direction, without using PBC along the field direction several times. Now, let N_L^α ($\alpha \in [x, y, z]$) denote the areal density of connected vortex paths threading the system in any direction, including the direction parallel to the induction. It is clear that in the Abrikosov vortex lattice phase $O_L = 0$, and $N_L^z = B/\Phi_0$, while $N_L^x = N_L^y = 0$. Thus, N_L^α is a conserved quantity at fixed induction B . On the other hand, $O_L = 1$ implies that $N_L^{x,y} > 0$, and the *total* number of vortex paths threading the system in any direction scales with system size, but undergoes thermal fluctuations. Therefore, N_L^α is no longer a conserved quantity.

We propose the following scenario to interpret the change in O_L and N_L^α . Number conservation uniquely identifies a $U(1)$ -symmetry, and hence the low-temperature phase of the *vortex*-system (the dual of the phase-representation of the superconductor) exhibits explicit $U(1)$ -symmetry, since $O_L = 0$. At high temperatures $O_L = 1$, N_L^α is not conserved, and the $U(1)$ -symmetry is broken. A $U(1)$ -symmetric phase cannot be analytically continued to a $U(1)$ -nonsymmetric one. The change in O_L from 0 to 1 could therefore signal a phase-transition, in this case involving breaking a global $U(1)$ -symmetry, in finite as well as zero magnetic field. However, to substantiate such a claim, one needs to argue that O_L is related to a local order parameter of the system. To this end, we note that it is possible to transcribe the *vortex-part* of the Ginzburg-Landau theory in the phase-only approximation in such a way that the vortex-part of the theory is specified in terms of a local, complex matter field $\phi(\mathbf{x})$, and that the theory then *explicitly* exhibits a $U(1)$ -symmetry¹⁶. In the Lattice London Model, corresponding to the Villain-approximation to the Ginzburg-Landau theory, this symmetry is therefore only *implicit*, or “hidden”. The probability of finding a connected vortex-path starting at a point \mathbf{x} and ending at point \mathbf{y} , $G(\mathbf{x}, \mathbf{y})$, is given in terms of the two-point correlation function of the matter field $\phi(\mathbf{x})$, $G(\mathbf{x}, \mathbf{y}) = \langle \phi^*(\mathbf{x}) \phi(\mathbf{y}) \rangle$ ¹⁶. O_L may be viewed as a special case of G , and in the thermodynamic limit corresponds to $\lim_{|\mathbf{x}-\mathbf{y}| \rightarrow \infty} G(\mathbf{x}, \mathbf{y})$. If $G(\mathbf{x}, \mathbf{y})$ is non-zero in this limit, this *suggests* the possibility of having $\langle \phi(\mathbf{x}) \rangle \neq 0$, and hence a broken $U(1)$ -symmetry. Although this does not constitute a proof that O_L is

connected to a local order parameter whose expectation value is associated with a broken $U(1)$ -symmetry, it seems to be suggestive of such a phase-transition existing even at finite magnetic field. Note that the above local matter field ϕ appears to be the dual field of a complex order parameter appearing in a somewhat different independent approach to the same problem by Tešanović¹⁷.

III. RESULTS AND DISCUSSION

In this section, we discuss the results of our simulations on an isotropic system with size of 120^3 grid points, which is the largest to date on an isotropic system. The system is subdivided into multiple sections, and the Monte Carlo procedure is implemented in parallel across the sections using 3D “black and white” decomposition⁶. The filling fraction considered are $1/f = 20, 40, 60$, and ∞ . The system is cooled from high temperatures. For each temperature, a typical run consists of 120000 Monte Carlo sweeps across the whole lattice, 1/3 of that were used for equilibration. Near phase-transitions, up to 600000 sweeps were used.

In Fig. (1), we present the results for the zero-field case, $f = 0$, where we show the specific heat C , the superfluid stiffness Υ , and the vortex-path probability O_L as functions of temperature. Note how the specific heat anomaly, the vanishing of the superfluid stiffness and O_L , all coincide with $\tilde{T}_c \approx 2.20$. The physical interpretation of $O_L = 1$ is that the effective long-wavelength vortex-line tension vanishes^{4,6,17}. This claim is substantiated by calculating the probability distribution $D(p)$ of vortex loops as a function of perimeter p , at various temperatures. We may fit this distribution to the form¹⁸

$$\begin{aligned} D(p) &= A p^{-\alpha} e^{-\beta \varepsilon p}; \quad T < T_c \\ &= A p^{-\alpha}; \quad T \geq T_c \end{aligned} \quad (7)$$

where ε is an effective, *temperature dependent*, long-wavelength line tension, $\beta = 1/k_B T$, and $\alpha = 5/2$. The results are shown in Fig. (2), demonstrating that at $T = T_c$, a purely algebraic decay is realized, implying $\varepsilon = 0$. Below T_c , the exponential decay is well fitted, showing that $\varepsilon \neq 0$. The inset of Fig. (2) shows ε as a function of temperature, as obtained in our simulations. A similar method of extracting ε for the zero-field case using a similar form for $D(p)$ (without the power-law prefactor) has previously been used by Li and Teitel, in Ref. 19.

The results for the quantities $S(\mathbf{k})$, Υ and C for $1/f = 20$ are shown in Fig. (3). Similar qualitative features are also found for the cases $1/f = 40, 60$. First, $S(\mathbf{k}_\perp)$ exhibits six-fold Bragg peaks at low temperatures (not shown). This indicates that the low temperature phase is a triangular vortex lattice phase. The destruction of the vortex lattice structure is marked by a melting transition at $\tilde{T}_m \approx 1.34$ where $S(\mathbf{k}_1)$ drops sharply to zero, where \mathbf{k}_1 is the wavevector of one of the six first

order Bragg peaks. The sharpness of the drop in $S(\mathbf{k}_1)$ strongly suggests that the transition is first order. This is confirmed by the appearance of a δ -function like peak in C at the same temperature \tilde{T}_m . Coincidentally, Υ_{\parallel} which is finite at low temperatures, also drops sharply to zero at \tilde{T}_m . *The isotropic system exhibits longitudinal superconductivity below \tilde{T}_m , but not above.* Moreover, based on our above discussion in Section II, we interpret the rise in the quantity O_L from 0 to 1 as signalling that the effective long-wavelength vortex-line tension vanishes. Thus, the vortex liquid phase is divided into two regions in phase-space. In one region, the vortex liquid is phase-incoherent i.e. has no longitudinal superfluid density but has finite vortex-line tension. We *propose* that this phase exhibits a vortex-associated $U(1)$ -symmetry. In the other region the vortex liquid is phase-incoherent but has zero vortex-line tension. We propose that this phase exhibits a broken $U(1)$ -symmetry.

Based on this, one can conclude that a first order melting transition of the Abrikosov vortex lattice exists in an *isotropic* system in the absence of pinning. The entire vortex liquid phase is *incoherent*, i.e. a vortex liquid phase with no longitudinal superconductivity. Note that the same conclusion has been reached in earlier simulations on *anisotropic* systems^{5,4,6}. There have been earlier reports of a disentangled vortex liquid, i.e. vortex liquid with non-zero longitudinal phase coherence. These results have been obtained in similar simulation¹⁰⁻¹². In Ref. 12, it was argued that a phase-coherent vortex liquid should be most easily observed in isotropic systems for $f \leq 1/18$. However, these simulations were performed on comparatively small systems, typically of sizes no larger than 24^3 . Our present results are based on much larger systems, 120^3 . We have observed a slight difference in the temperatures at which $S(\mathbf{k})$ and Υ_{\parallel} vanish in simulations on smaller system or lower number of sweeps. Therefore, it may be concluded that the existence of a vortex liquid with a nonzero longitudinal superfluid density is a numerical artifact of small system sizes and/or insufficient simulation time²⁰. It is well understood that the λ -transition is driven by proliferation of thermally excited loops of all sizes. In recent work by some of us, it was proposed that the same mechanism is driving the first order melting transition at low B and a newly discovered continuous transition involving the breaking of $U(1)$ symmetry at large B ⁶.

Similar results for $1/f = 40$ and 60 enable us to propose a simple phase diagram for an isotropic extreme type-II superconductor in the absence of disorder (see Fig. (4)). Immediately below and above the \tilde{T}_m line, the phases of the vortex system are identified as the Abrikosov vortex lattice and the incoherent vortex liquid, respectively.

In a pin-free system, one would expect Υ_{\perp} to be zero at all temperature. In this case, the numerical lattice, on which simulations are performed, effectively pins the vortex lines from moving in the transverse plane and coun-

teracts the Lorentz forces on them in the presence of a transverse applied current. However, the pinning is overcome by thermal fluctuations at higher temperature and the vortex lines are depinned at temperature $\tilde{T}_d \approx 0.62$. Fortunately, we see that $\tilde{T}_d \ll \tilde{T}_m$, which means that near \tilde{T}_m , the vortex lines, and the melting process, are completely free from the effects of the numerical grid. Therefore, the features of C , Υ_{\parallel} and $S(\mathbf{k})$ at \tilde{T}_m are genuine thermodynamic effects.

IV. CONCLUSION

We have performed simulations of the uniformly frustrated 3DXY model on a large *isotropic* system (120^3 grid points) for a variety of filling fractions $1/f = 20, 40, 60$ and ∞ . We found a first order melting transition in this isotropic system for all the three non-zero values of f considered. The longitudinal phase coherence and triangular crystalline order of the Abrikosov vortex crystal are simultaneously destroyed at the melting transition. Above the melting temperature, the incoherent vortex liquid is the only thermodynamic phase. We have demonstrated that previous claims of the existence of disentangled vortex liquid¹⁰⁻¹² is due to performing simulations using insufficient system sizes and simulation times.

We have shown that the effective vortex-line tension vanishes precisely at the zero-field superconducting transition. The loss of superfluid stiffness, the loss of line tension, and the abrupt change in the connectivity of the vortex tangle, as signalled by the change in the quantity O_L across the system, all coincide in this case. A similar change in connectivity across the vortex system takes place at finite magnetic field. The results of the Ref. 15, the present paper, and in particular those of Ref. 6 strongly indicate that this change in connectivity is sharp in the limit of large systems, thus indicating the loss of number-conservation of connected vortex paths threading the system. Since the finite probability of finding a connected vortex path threading the system in a direction other than the magnetic field may be tied to the finite expectation value of a local complex matter field¹⁶, this lends further support to the argument that the change in O_L signals the breaking of a $U(1)$ -symmetry²¹. At the very least this proposition appears to be intriguing enough to warrant further investigation.

We finally caution the reader that we so far have not been able to detect any anomaly in specific heat at the suggested new finite-field transition inside the vortex liquid, for the isotropic case. Even the anomaly at the first order melting transition is weak in the isotropic case, and is difficult to bring out in simulations. It may be that considerably larger systems are needed for the isotropic case in order to see signals in the specific heat of the suggested new transition due to the small amount of entropy in the transition. This is the reason why the anomaly at the first order vortex lattice melting transi-

tion is difficult to observe in simulations. It is conceivable that increasing the anisotropy of the system should bring out the anomaly clearer, if it exists. This indeed is the case for the anomaly at the vortex lattice melting transition. A weak anomaly associated with the putative $U(1)$ -transition, may in fact have been observed for the anisotropic case in Ref. 6.

ACKNOWLEDGMENT

We thank J. S. Høye, P. Olsson, S. Teitel, and Z. Tešanović for discussions and constructive remarks. This work is supported by the Norges Forskningsråd under grants 115577/410, 110566/410 and 110569/410. We acknowledge the use of the Cray T3E-600 at the Norwegian Supercomputing Project of NTNU, Trondheim, Norway.

-
- ¹ J. G. Bednorz and K. A. Müller, Z. Phys. **B64**, 189 (1986).
 - ² A. A. Abrikosov, Zh. Eksp. Teor. Fiz.[Sov. Phys. JETP] **5**, 1174 (1957).
 - ³ A. K. Nguyen and A. Sudbø, Phys. Rev. B **57**, 3123 (1998).
 - ⁴ A. K. Nguyen and A. Sudbø, Phys. Rev. B **58**, 2802 (1998).
 - ⁵ X. Hu, S. Miyashita, and M. Tachiki, Phys. Rev. Lett. **79**, 3498 (1997).
 - ⁶ A. K. Nguyen and A. Sudbø, cond-mat/9811149.
 - ⁷ H. Nordborg and G. Blatter, Phys. Rev. Lett. **79**, 1925 (1997).
 - ⁸ J. Hu and A. H. MacDonald, Phys. Rev. B **56**, 2788 (1997).
 - ⁹ D. López, E. F. Righi, G. Nieva, and F. de la Cruz, Phys. Rev. Lett. **76**, 4034 (1996).
 - ¹⁰ Y.-H. Li and S. Teitel, Phys. Rev. Lett. **66**, 3301 (1991); Phys. Rev. B **47**, 359 (1993).
 - ¹¹ T. Chen and S. Teitel, Phys. Rev. B **55**, 11766 (1997); Phys. Rev. B **55**, 15197 (1997).
 - ¹² S. Ryu and D. Stroud, Phys. Rev. B **57**, 14476 (1998).
 - ¹³ R. E. Hetzel, A. Sudbø, and D. A. Huse, Phys. Rev. Lett. **69**, 518 (1992).
 - ¹⁴ J. J. Binney, N. J. Dowrick, A. J. Fisher, and M. E. J. Newman, *The Theory of Critical Phenomena: An Introduction to the Renormalization Group* (Clarendon Press, Oxford, 1992).
 - ¹⁵ A similar quantity as O_L has previously been considered by E. A. Jagla and C. A. Balseiro, Phys. Rev. B **53**, 538 (1996). These authors calculated the connectivity of a vortex tangle in a high-temperature superconductor and concluded that the connectivity changed as a result of a percolation transition taking place in the *vortex lattice*, considering systems that were much smaller than in the present paper. They did not attempt to identify any broken symmetry with the suggested transition, and concluded that this percolation transition was *necessary* in order to have dissipation in the c-direction. However, as the present results show, and as the results of Ref. 6 show, it is not necessary to have a percolation transition to destroy longitudinal superfluidity. The change in O_L is *preempted* by the loss of longitudinal phase-coherence and onset of longitudinal dissipation. We believe these results are a consequence of too short simulation times, possibly on too small systems. For finite-size effects on T_L , see Fig. 2 of Ref. 6, where systems considerably larger than those of Jagla *et al.* were considered.
 - ¹⁶ H. Kleinert, *Gauge-fields in Condensed Matter*, Vol. 1, Ch. 6, World Scientific Press, Singapore, (1998). See also M. Kiometzis, H. Kleinert, and A. M. Schakel, Fortschr. Phys. **43**, 697 (1995).
 - ¹⁷ Z. Tešanović, Phys. Rev. B **51**, 16204, 1995; cond-mat/9801306.
 - ¹⁸ We thank J. S. Høye for helpful discussions on this point. A similar functional form for $D(p)$ involving the effective line tension, i.e. the free energy per unit length of a vortex line, is to our knowledge not available for the finite-field case and we have been unable to carry out a similar analysis when the field is non-zero.
 - ¹⁹ Y.-H. Li and S. Teitel, Phys. Rev. B **47**, 359, (1993); *ibid* **B 49**, 4136 (1994). These authors concluded that the loss of line tension at finite field is associated with the loss of longitudinal phase coherence. The present work, as well as that of Refs. 5,6, shows that this is not correct. The longitudinal phase-coherence vanishes at the melting transition of the vortex lattice. This is related to the comments made above, in Ref. 15.
 - ²⁰ Similar results as the ones we have obtained for the longitudinal phase coherence in the vortex liquid phase in this paper, have now been reported by P. Olsson and S. Teitel, cond-mat/9810169.
 - ²¹ It is not excluded that the $U(1)$ -symmetry proposed here may be broken in a first order phase transition even in the absence of gauge-fluctuations, in a finite magnetic field. For the zero-field case this is known to happen provided gauge-fluctuations are taken into account, see B. I. Halperin, S. K. Ma, and T. C. Lubensky, Phys. Rev. Lett., **32**, 292 (1974); I. F. Herbut, Z. B. Tešanović, Phys. Rev. Lett. **76**, 4588 (1996); *ibid*, **78**, 980 (1997).

FIG. 1. Specific heat C , superfluid stiffness Υ , and vortex-path probability O_L for $\Gamma = 1$, $f = 0$.

FIG. 2. Vortex-loop probability distribution $D(p)$ as a function of loop-perimeter p for various temperatures, $\Gamma = 1$, $f = 0$. The lines in the figure are fits using $D(p) = A p^{-\alpha} \exp(-\beta \varepsilon p)$, with $A = 1$, $\alpha = 5/2$, and $\beta = 1/k_B T$. ε is the only fitting parameter in all plots. The inset shows the effective long-wavelength vortex-line tension ε . The solid line is a guide to the eye. ε vanishes at $T = T_c$. Here, ξ is the grid-spacing of the numerical lattice, and serves both as a unit of length and a measure of the superconducting coherence length.

FIG. 3. Specific heat per site C , helicity moduli Υ_{\perp} and Υ_{\parallel} , vortex-path probability O_L , and structure factor $S(\mathbf{k}_1)$ (where \mathbf{k}_1 is the wavevector for one of the first order Bragg peak) as a function of \tilde{T} for a system size $V = 120^3$ and $1/f = 20$. The melting temperature $\tilde{T}_m \approx 1.34$ is marked by the sharp drop of $S(\mathbf{k}_1)$. The coincidence of a sharp peak in C at \tilde{T}_m confirms that the melting phase transition is first order. Υ_{\parallel} also vanishes at \tilde{T}_m indicating that the triangular vortex crystal melts into an incoherent vortex liquid. At $\tilde{T} \approx 1.90$, O_L jumps from 0 to 1, signalling a $U(1)$ -symmetry breaking, or equivalently a $3DXY$ -transition.

FIG. 4. The intrinsic $f - \tilde{T}$ phase diagram of an isotropic system based on simulations on system size $V = 120^3$ and $f = 0, 1/20, 1/40$ and $1/60$. The first order melting-line and the $3DXY$ -line are denoted by \tilde{T}_m and \tilde{T}_L , respectively.

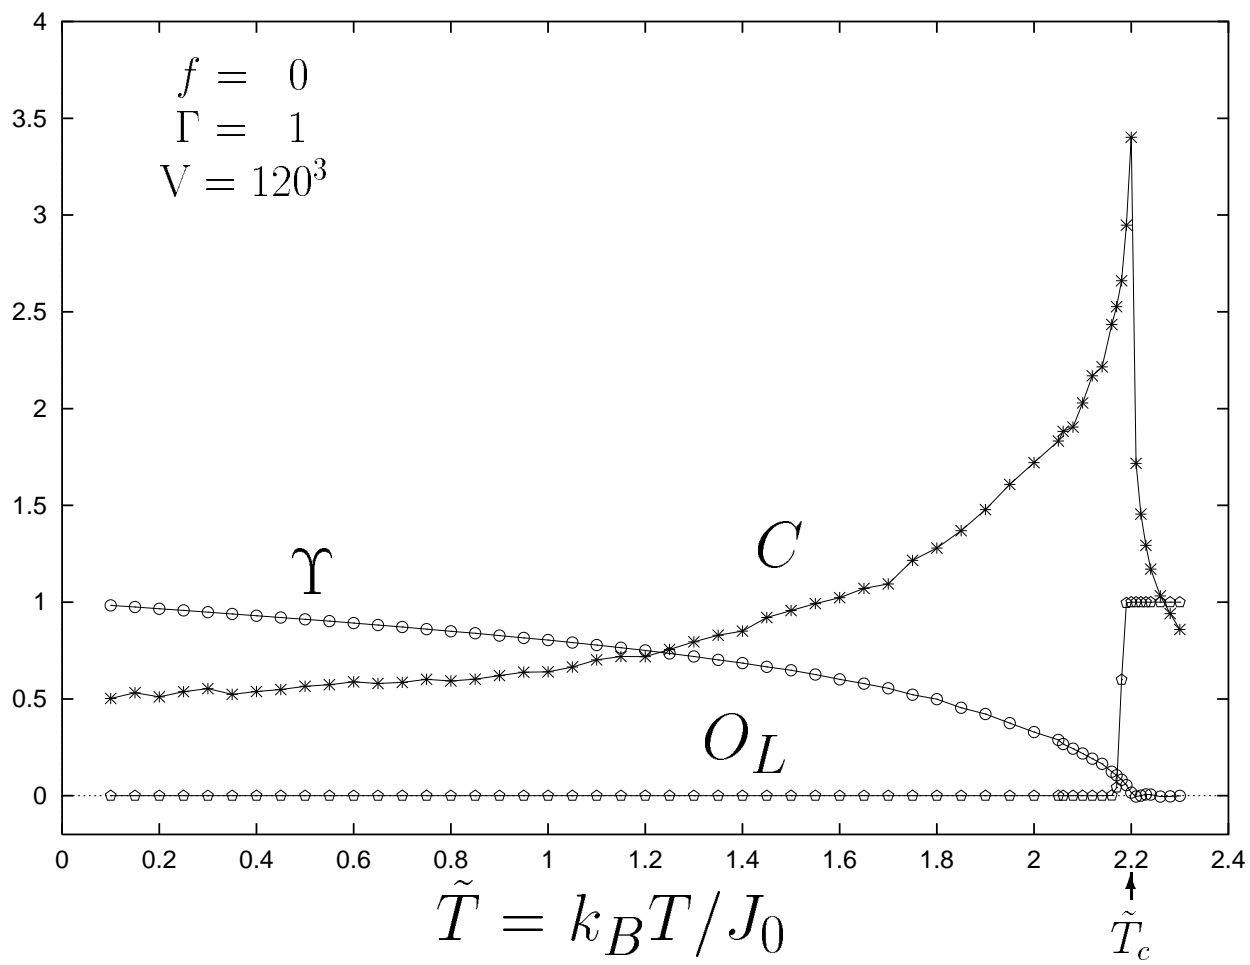


Figure 1

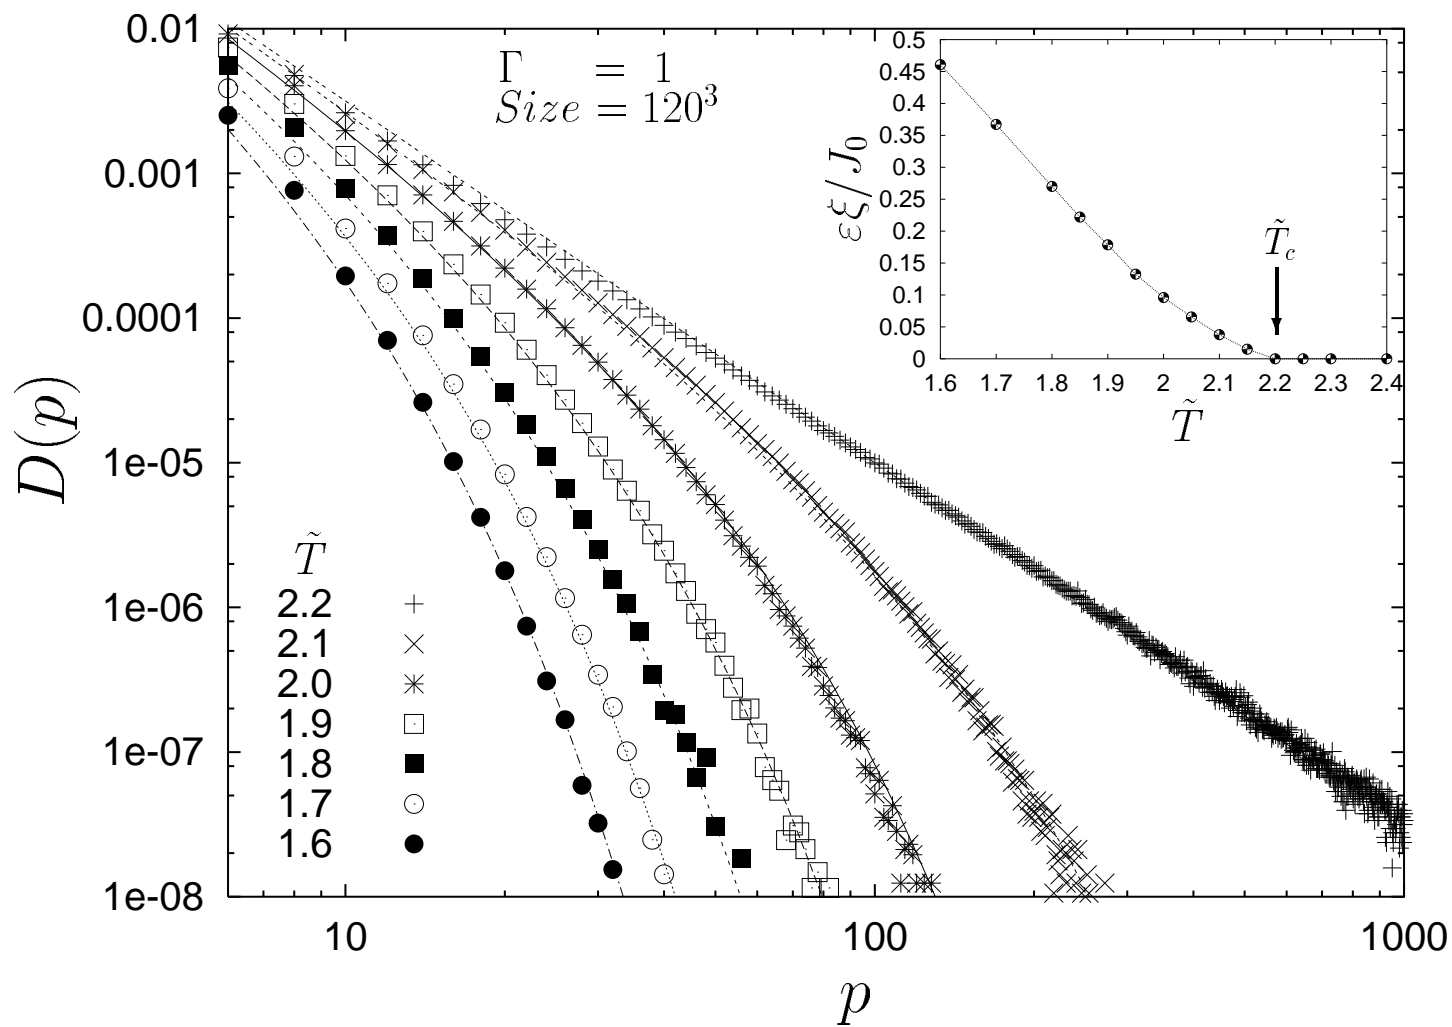


Figure 2

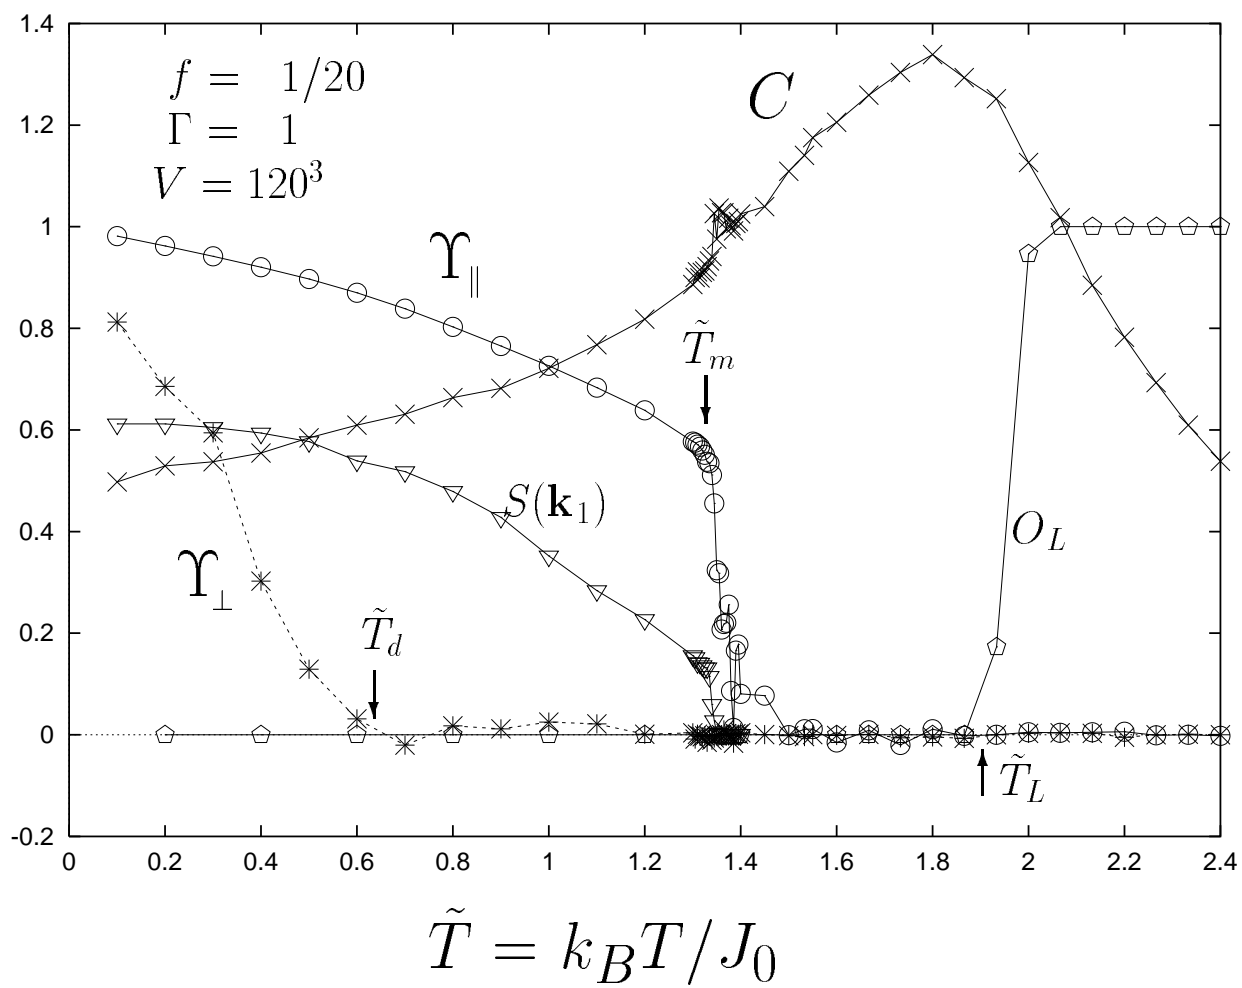


Figure 3

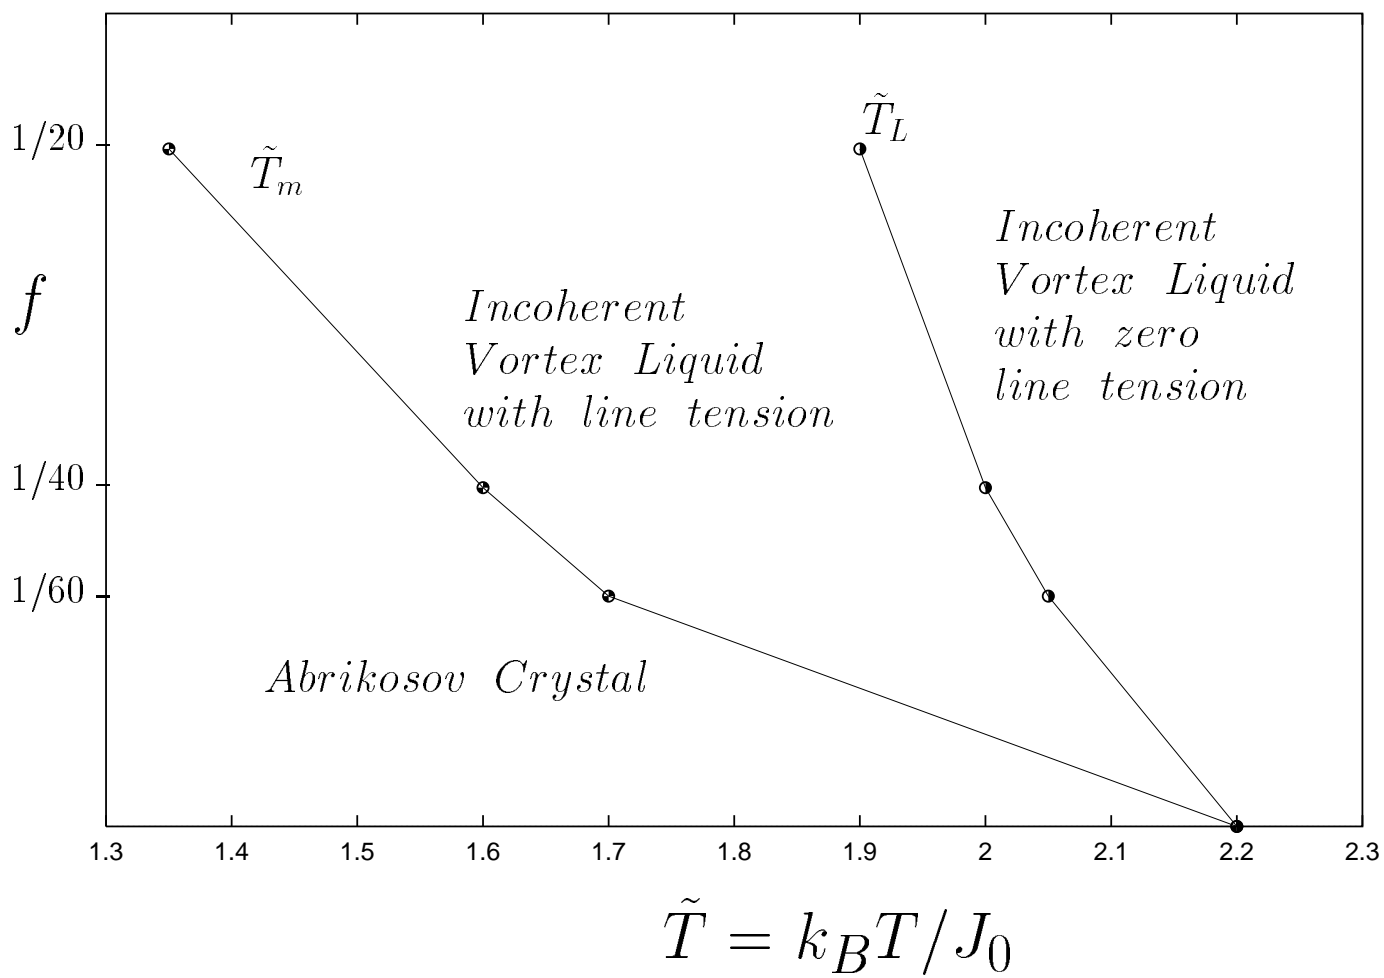


Figure 4